

NEPHELINE

A. N. WINCHELL, *University of Wisconsin, Madison, Wisconsin.*

In 1912 Bowen¹ produced pure sodium nepheline artificially and measured its optical properties; he also showed that it could take into crystal solution as much as 35 per cent of the materials of anorthite; with increase in the tenor of these constituents he showed that the index, N_o , remained constant at 1.537, while N_e increased from 1.533 to 1.539, thus changing the optic sign from minus to plus. In 1917 he showed² that NaAlSiO_4 can intercrystallize *at a high temperature* with all proportions of KAlSiO_4 . In 1931 Bannister and Hey³ made it clear that at low temperatures no more than about 30 per cent of KAlSiO_4 is stable in NaAlSiO_4 . In 1933 the writer suggested⁴ that (in harmony with atom for atom explanation of crystal solution) $\text{CaAl}_2\text{Si}_2\text{O}_8$ does not intercrystallize with NaAlSiO_4 , but that its components, CaAlAlO_4 and SiSiO_4 , do so. Bowen himself reported in 1912 that NaAlSiO_4 can take into crystal solution at least as much as 5 per cent of SiSiO_4 ; so far as known to the writer no tests of the solubility of CaAlAlO_4 in NaAlSiO_4 have been made. It seems probable that if it is soluble it would increase the density and refractive index. Is it because SiSiO_4 would leave a vacancy in the structure and therefore lower the density and index that the combination of these two does not change the index (for the ordinary ray)?

In an attempt to solve the problem of the constitution of nepheline, the writer has made a rather detailed study of recent analyses of the mineral, with special reference to those which are accompanied by determinations of the physical properties. The results seem to be significant. The analyses in question have been calculated into NaAlSiO_4 , KAlSiO_4 and other formulas which imply atom for atom replacement, that is, CaAlAlO_4 , SiSiO_4 , $\text{AlSiO}_3(\text{OH})$ and CaCaSiO_4 . The last one of these is the least satisfactory; perhaps impurities or inaccuracies of analysis are sufficient to render it unnecessary. The results are assembled in the following table.

¹ Bowen, N. L., *Am. Jour. Sci.*, **33**, 49 and 551 (1912).

² Bowen, N. L., *Am. Jour. Sci.*, **43**, 115 (1917).

³ *Min. Mag.*, **22**, 569 (1931).

⁴ Optical Mineralogy, Part 2, 299 (1933).

TABLE 1. COMPOSITION OF NEPHELINES IN MOLECULAR PER CENT OF NaAlSiO_4 , KAlSiO_4 , CaAlAlO_4 , SiSiO_4 , $\text{AlSiO}_3(\text{OH})$ AND CaCaSiO_4 AS CALCULATED FROM RECENT ANALYSES

No.	NaAlSiO_4	KAlSiO_4	CaAlAlO_4	SiSiO_4	$\text{AlSiO}_3(\text{OH})$	CaCaSiO_4
A	100.0 (artificial)					
1	75.0	9.6	5.6	9.3		0.4
2	69.5	12.0	4.8	9.2	4.5	
3	64.2	14.5	4.8	9.1	7.4	
4	53.2	14.8	11.2	14.5	6.2	
5	74.5	15.6	2.3	7.1		0.4
6	69.0	16.2	5.5	7.3	2.0	
7	68.3	17.4	3.8	10.4		
8	55.1	23.0	1.8	17.9		2.2
9	64.2	26.5	5.5	1.9		2.0
10	81.2	14.6		2.4		1.8
11	60.2	35.2	1.0	2.4		1.2
12	73.0	11.8	1.4	13.0		0.7
13	68.1	20.2	1.2	3.3	7.2	
14	77.6	13.1	1.9	7.1		0.3
15	79.1	16.7		2.7		1.4
16	61.9	32.2	1.7	1.7		2.6
17	68.0	17.7	5.5	8.7		
18	77.8	10.9	2.2	9.0		
19	68.0	17.3	2.0	2.5	10.2	
20	75.9	14.3	1.7	8.1		

References for Table 1 and Figs. 1, 2, 3.

- A. Bowen, N. L.: *Am. Jour. Sci.*, **33**, 49 (1912). A in Fig. 2 derived from Fig. 1.
- 1-9. Bannister, F. A., and Hey, M. H.: *Min. Mag.*, **22**, 569 (1931).
10. Dunham, K. C.: *Am. Mineral.*, **18**, 369 (1933).
- 11, 12. Bowen, N. L., and Ellestad, R. B.: *Am. Mineral.*, **21**, 363 (1936).
13. Walker, T. L., and Parsons, A. L.: *Univ. Toronto Geol. Stud.*, **21**, 8 (1925).
- 14-15. Zambonini, F.: *App. Mineral. Vesuvius and Rend. Accad. Fis. Mat. Napoli*, **15**, 26 (1912). Abst. in *Zeits. Krist.*, **55**, 301 (1915).
16. Zambonini, F.: *Rend. Accad. Fis. Mat. Napoli*, **49**, 83 (1910). Abst. in *Zeits. Krist.*, **52**, 313 (1913).
17. Starraba, F. S.: *Riv. Min. Crist. Ital.*, **48**, 53 (1917); *Min. Abst.* **I**, 108.
18. Washington, H. S., and Merwin, H. E.: *Jour. Wash. Acad. Sci.*, **5**, 389 (1915).
19. Walker, T. L., and Parsons, A. L.: *Univ. Toronto Geol. Stud.*, **22**, 5 (1926).
20. Barth, T.: *Vid. Akad. Oslo*, No. 8, 66 (1927).

If the components of nepheline were NaAlSiO_4 , KAlSiO_4 and $\text{CaAl}_2\text{Si}_2\text{O}_8$, then the percentages of CaAlAlO_4 and SiSiO_4 would be equal in each analysis. Such a condition is found in only one analysis (16); in one case (9) CaAlAlO_4 is nearly three times as abundant as SiSiO_4 , but in most cases SiSiO_4 is two to six times as plentiful as CaAlAlO_4 . Of course this may be due to imperfections in the analyses, but such large discrepancies are somewhat surprising.

If nepheline contains all of these components (or even the first four), it is clear that there can be no simple relation between the tenor of KAlSiO_4 and the physical properties, since the latter must depend upon all of the components. To obtain an approximation of the properties in the NaAlSiO_4 - KAlSiO_4 series those analyses with the least amounts of other components are used. In Fig. 1 all those analyses which contain at

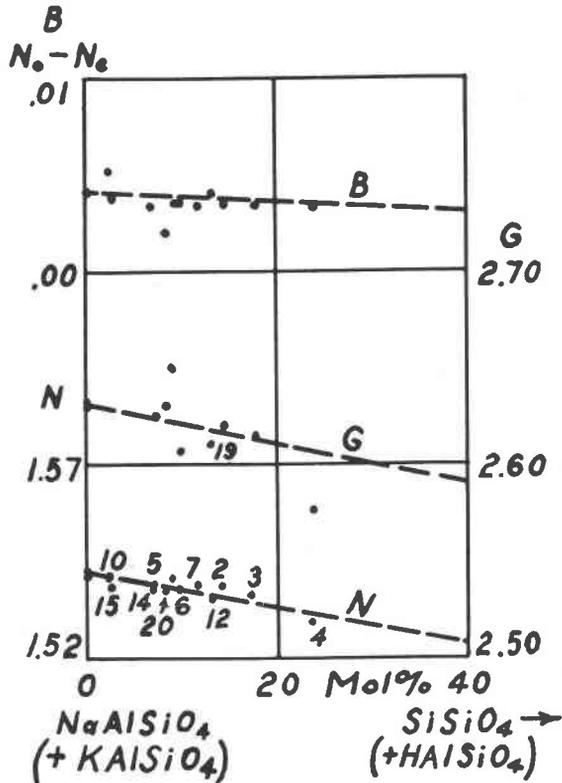


FIG. 1

least 90 per cent of NaAlSiO_4 + KAlSiO_4 are recorded. The results are reasonably concordant except for the specific gravity of No. 16. Since the refractive index of 16 falls on the line, it seems probable that the specific gravity is somewhat in error.

Is it possible to find any correlation between the content of SiSiO_4 (+ HAlSiO_4) and the physical characters? If all the analyses containing

about 15 per cent of KAlSiO_4 (exactly 11.8–17.7) are plotted on the basis of their tenor of SiSiO_4 , as in Fig. 2, it is clear that the refractive index and specific gravity decrease with increase of this component. This condition is in harmony with the idea that the presence of SiSiO_4 implies a vacant position (occupied by the alkali atom in the usual structure). The fact that the decrease is not as rapid as required by assuming such vacant positions is perhaps due to the presence of water in them. Nearly all of these analyses show that water is present in small amount.

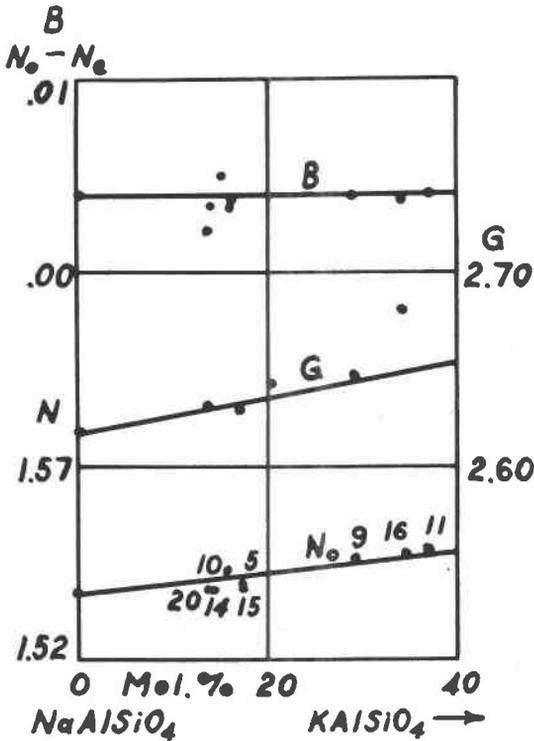


FIG. 2

Finally, in Fig. 3, an attempt is made to show the effects of both of these variables in one diagram. But the data are insufficient to give more than a first approximation, and such a diagram can never be more than an approximation because other variables (notably Ca) are disregarded. Figure 3 shows clearly that SiO_2 and K_2O vary quite independently of each other.

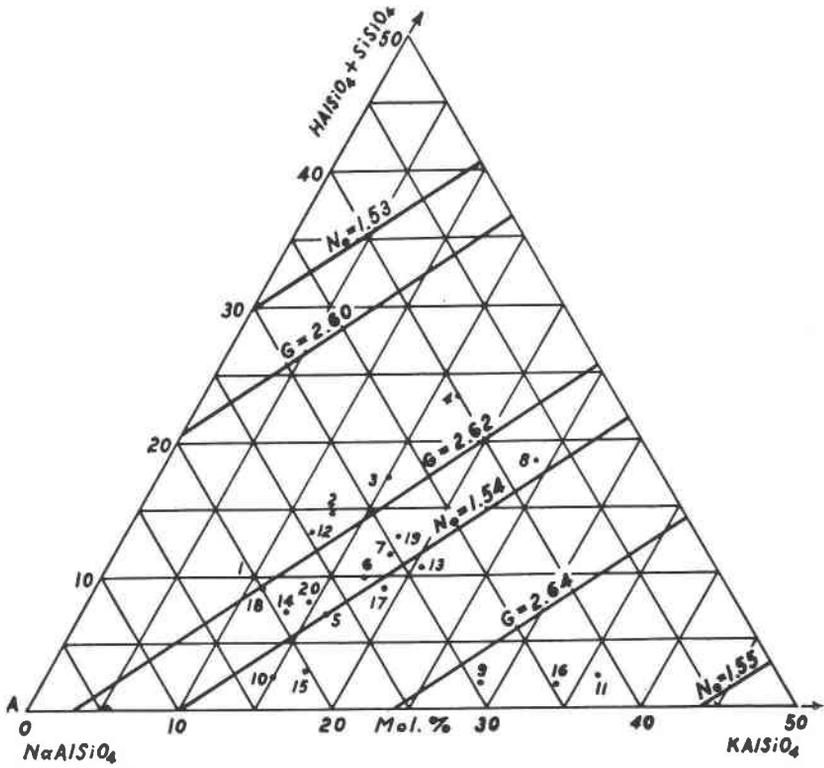


FIG. 3